





UN38.3 TEST REPORT UN38.3 检测报告

Report No.:

报告编号:

CMC220609011-1

Name of Goods:

物品名称:

Rechargeable Lithium-ion cell

可充电锂离子电芯

Model:

型号:

18650

Type:

规格:

3.7V 1500mAh 5.55Wh

Client:

委托单位:

Classification

of test:

检测类别:

Commission Test

委托检测

Tested by:

Riley Xian 南芝

Approved by:

批准人:

Inspected by:

审核人:

Dylan Dou Z Mid

Date of Issue:

签发日期:

2022.07.14

Seal of CMC:

CMC 印章:



CMC Testing International (Shenzhen) Co., Ltd.

众检检验认证(深圳)有限公司

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 Version: A/2.1

400-1668-320

info@cmczj-lab.com

www.cmczj-lab.com

1 / 17



TEST REPORT

检测报告

Name of Goods 物品名称	Rechargeable Lithium-ion cell 可充电锂离子电芯		m-ion cell Model 쪂무		18650	
Commissioner 委托单位	消	消				
Commissioner's Address 委托单位地址	i''			5 	-	
Manufacturer 制造商			1000			
Manufacturer's Address 制造商地址	(f'					
Manufacturer's Contact Telephone		-	E-mail 邮箱			
制造商联系电话	hage to		Web 网址			
Trade Mark/ identification 商标/识别码		Shape 形状	Cylinder 圆柱体	Size 尺寸 (D×H)	(18.4×65.5) mm	
Nominal Voltage 标称电压	3.7V	Charge Voltage 充电电压	4.2V	Rated Capacity 额定容量	1500mAh	
Nominal Charge Current 标称充电电流	750mA	Maximum Charge Current 最大充电电流	750mA	End of Charge Current 结束充电电流	30mA	
Nominal Discharge Current 标称放电电流	750mA	Maximum Discharge Current 最大放电电流	750mA	Discharge Cut-off Voltage 放电截止电压	3.0V	
Cell Model 电池型号	18650	Cell Nominal Voltage 电池标称电压	3.7V	Cell Rated Capacity 电池额定容量	1500mAh	
Cells Number 电池数量	1PC	Sample Receiving Date 样品接收日期	2022.06.09	Testing Date 测试日期	2022.06.09 — 2022.06.23	
Test conclusion 检测结论	The test result 检测结果为合格	s are qualified. 洛。				

400-1668-320

info@cmczj-lab.com

www.cmczj-lab.com



Test Standard 检测标准

UN "Manual of Tests and Criteria" ST/SG/AC.10/11/Rev.7/Subsection 38.3

联合国《试验和标准手册》 (第7版) 38.3节

Description and illustration of the sample: The sample's status is good.

样品说明及描述: 样品状况良好。

Test item 检测项目	Sample No. 样品编号	State 状态	Remark 备注
Test 1 ~ Test 5	C001~C005	First cycle fully charged 第一个充电周期,完全充电	
1631 1 1631 3	C006~C010	25 cycles fully charged 第25个充电周期,完全充电	
	C011~C015	First cycle 50% Capacity 第一个充电周期,50%容量	
Test 6	C016~C020	25 cycle 50% Capacity 第25个充电周期,50%容量	
Test 7	-		_
	-		
Test 8	C021~C030	First cycle fully charged 第一个充电周期,完全放电	
	C031~C040	25 cycles fully charged 第25个充电周期,完全放电	

CXXX is used as the sample number of cells SN220609011CXXX, "X" is 0~9. CXXX 代表电芯样板编号 SN220609011CXXX, X=0~9。

Description of the deviation fr 检测结果不符合标准项的说明	
Test environment conditions: 检测环境条件:	20±5°C
Remarks: 备注:	

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 Version: A/2.1

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 3 / 17



38.3.4.2

Test 2: Thermal test

起火现象的发生。

Report No.: CMC220609011-1

	ST/SG/AC.10/11/Rev.7/Section 3	8.3	
Clause 章节	Requirements 标准要求	Result 测试结果	Verdict 判定
38.3.4	Procedure 检测步骤		
38.3.4.1	.4.1 Test 1: Altitude simulation 检测 1: 高度模拟		
	Test cells and batteries shall be stored at a pressure of 11.6kPa or less for at least six hours at ambient temperature (20±5°C). 将电池和电池组在温度为 20±5°C,大气压力为不大于 11.6kPa 的环境中贮存不少于 6 小时。		
	Requirements 标准要求: 1) Cells and batteries Mass loss limit reference: Table 38.3.1 样品质量损失限值参考:表 38.3.1 2) Open circuit voltage not less than 90%, The requirement relating to voltage is not applicable to test cells and batteries at full discharged states. 样品试验后开路电压应不低于试验前开路电压的 90%,此要求不适用于完全放完电的电池或电池组。 3) No leakage, no venting, no disassembly, no rupture and no fire.样品(电池)应无渗漏、无排气、无解体、无破裂以及无起火现象的发生。	The samples C001~C010: No leakage, no venting, no disassembly, no rupture and no fire. 编号为 C001~C010 的样品: 无渗漏、无排气、无解体、无破裂以及无起火现象。 The data is shown in Test T.1 数据见表 T.1	Pass 合格

检测 2: 温度试验	
Test cells and batteries are to be stored for	
电池和电池组存储条件如下:	
1) For small cells and batteries: one temperature cycle: 72±2°	C <mark>(6h) ~ -</mark> 40±2°C (6h)
对于小型电池和电池组:一次温度循环为 72±2°C (6h) ~ -40±2	.°C (6h)
For large cells and batteries: one temperature cycle: 72±2°C (12h) ~ -40±2°C (12h)
对于大型电池和电池组: 一次温度循环为 72±2°C (12h) ~ -40±	:2°C (12h)
2) The maximum time interval between test temperature extre	mes is 30minutes.
温度转换最大间隔时间为 30min。	
3) This procedure is to be repeated 10 times. 重复 10 次循环	
4) after which all test cells and batteries are to be stored for 24	
(20±5°C). 循环结束后,电池和电池组在 20±5°C 的条件下搁置	是 24 小时。
Requirement 标准要求:	The samples C001~C010:
1) Cells and batteries Mass loss limit reference: Table 38.3.1	No leakage, no venting, no
样品质量损失限值参考:表 38.3.1	disassembly, no rupture and
2) Open circuit voltage not less than 90%, The requirement	no fire. 编号为 C001~C010
relating to voltage is not applicable to test cells and batteries	的样品:无渗漏、无排气、无
at full discharged states.	解体、无破裂以及无起火现
样品试验后开路电压应不低于试验前开路电压的90%,此要求	象。
不适用于完全放完电的电池和电池组。	The data is shown in Table
小坦用 1 元主 以 元 电 的 电 他 和 电 他 组。	The data is shown in Table

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 Version: A/2.1

3) No leakage, no venting, no disassembly, no rupture and no fire. 样品(电池)应无渗漏、无排气、无解体、无破裂以及无

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 4 / 17

T.2 数据见表 T.2



	ST/SG/AC.10/11/Rev.7/Section 3	8.3	
Clause 章节	Requirements 标准要求	Result 测试结果	Verdict 判定
38.3.4.3	Test 3: Vibration 检测 3: 振动		
	を测 3: 振动 1) Cells and batteries are firmly secured to the platform of the vel地和电池组牢固地安装在振动台(的台面)上。 2) The vibration: a sinusoidal waveform with a logarithmic swed and back to 7Hz traversed in 15 minutes. 振动以正弦波形式,以 7Hz 增加至 200Hz,然后在减少回到 7H 15 分钟的对数前移传送。 3) For cells and small batteries: from 7Hz a peak acceleration is reached. The amplitude is then maintained at 0.8mm (1.6mm frequency increased until a peak acceleration of 8gn occurs (apacceleration of 8gn is then maintained until the frequency is incompared by the firm of 10 minutes acceleration of 8gn is then maintained until the frequency is incompared by the firm of 10 minutes acceleration of 20 minutes acceleration accelera	ep between 7Hz and 200Hz Hz 为一个循环,一个循环持续 of 1gn is maintained until 18Hz in total excursion) and the oproximately 50Hz). A peak creased to 200Hz. 不变,直到达到 18Hz。然后将 gn 的峰值加速度(大约 50Hz)。 ntained until 18Hz is reached. rsion) and the frequency ly 25Hz). A peak acceleration 0Hz. 直到达到 18Hz。然后将振幅保值加速度(大约 25Hz)。然后 of three mutually perpendicular must be perpendicular to the	Pass 合格

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 *Version: A/2.1*

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 5 / 17



	ST/SG/AC.10/11/Rev.7/Section 3	8.3	
Clause 章节	Requirements 标准要求	Result 测试结果	Verdict 判定
38.3.4.4	Test 4: Shock 检测 4: 冲击		
	1) Test cells and batteries shall be secured to the testing mach 以稳固的托架固定住每个电池和电池组样品的全部配件表面。 2) Each cell shall be subjected to a half-sine shock of peak acc duration of 6 milliseconds. Large cells may be subjected to a hacceleration of 50gn and pulse duration of 11 milliseconds. 对每个电池以峰值为 150gn 的半正弦的加速度撞击,脉冲持续 6度 50gn 和脉冲持续时间 11ms 的半正弦波冲击。 Small batteries shall be subjected to a half-sine shock of peak	celeration of 150g _n and pulse alf-sine shock of peak 6ms,大型电池须经受最大加速	
	Acceleration $(g_n) = \sqrt{\frac{100850}{mass}}$, which is smaller) aneration of $50g_n$ (
	which is smaller) and pulse dud pulse duration of 6 millisecond		
	subjected to a half-sine of peak accelration of 11 milliseconds.		
	对每个电池以峰值为 $150g_n$ (或与 $\sqrt{\frac{100850}{mass}}$ 中的 $$ 较小值)的半正弦	的加速度撞击,脉冲持续 6ms,	
	大型电池须经受最大加速度 $50g_n$ (或与 $\sqrt{\frac{30000}{mass}}$ 中的较小值)和版	永冲持续时间 11ms 的半正弦波	Pass
	冲击。 3) Each cell or battery shall be subjected to three shocks in the three shocks in the negative direction of three mutually perpenthe cell or battery for a total of 18 shocks. 每个电池或电池组须在三个互相垂直的电池安装方位的正方向经受三次冲击,总共经受 18 次冲击。	dicular mounting positions of	合格
	Requirements 标准要求: 1) Cells and batteries Mass loss limit: ≤0.2%. 样品质量损失≤0.2% 2) Open circuit voltage not less than 90%, The requirement relating to voltage is not applicable to test cells and batteries at full discharged states. 样品试验后开路电压应不低于试验前开路电压的 90%,此要求不适用于完全放完电的电池或电池组。 3) No leakage, no venting, no disassembly, no rupture and no fire. 样品(电池)应无渗漏、无排气、无解体、无破裂以及无起火现象的发生。	The samples C001~C010: No leakage, no venting, no disassembly, no rupture and no fire. 编号为 C001~C010 的样品: 无渗漏、无排气、无解体、无破裂以及无起火现象。 The data is shown in Table T.4 数据见表 T.4	

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 *Version: A/2.1*

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 6 / 17



	ST/SG/AC.10/11/Rev.7/Section 3	8.3	
Clause 章节	Requirements 标准要求	Result 测试结果	Verdict 判定
38.3.4.5	Test 5: External Short Circuit 检测 5: 外部短路		
	1) The cell or battery to be tested shall be heated for a period of homogeneous stabilized temperature 57±4°C. 加热电池或电池组样品直到温度稳定在 57±4°C 2) The cell or battery shall be subjected to a short circuit condition resistance of less than 0.1 ohm at 57±4°C, This short circuit condition one hour after the cell or battery external case temperature has 将样品正负极用小于 0.1Ω 的总电阻回路进行短路,样品的外表短路状态 1 小时以上。 3) The cell or battery must be observed for a further six hours to 对电池或电池组必须进一步观察 6 个小时才能下结论。	tion with a total external ndition is continued for at least s returned to 57±4°C. 温度恢复到 57±4°C 之后保持	Pass 合格
	Requirements 标准要求: 1) Cells external temperature not exceed 170°C. 电池的最高表面温度应不超过 170°C。 2) No disassembly, no rupture and no fire during the test and within six hours after the test. 测试中与测试后 6 小时内无解体、无破裂、无起火。	The samples C001~C010: No disassembly, no rupture and no fire. 编号为 C001~C010 的样品: 无解体、无破裂以及无起火现象。 The data is shown in Table T.5 数据见表 T.5	

38.3.4.6	Test 6: Impact / C <mark>rush</mark> 检测 6: 撞击/挤压		Pass 合格
	Impact (applicable to cylindrical cells not less than 18mm in dia 撞击(适用于直径 <mark>不小于 18 毫米的</mark> 圆柱形电池)	ameter)	
	1) This test sample cell or component cell is to be placed on a flat smooth surface. 将试验样品用的电池或元件电池放在一个平坦光滑的平面上 2) A 15.8 mm diameter bar is to be placed across the center of the sample, A 9.1kg mass is to be dropped from a height of 61±2.5cm onto the sample. 将一直径为 15.8mm 的不锈钢圆棒横过电池中部放置后,将一质量为 9.1kg 的物体从 61±2.5cm 的高度落向样品。 3) The test sample is to be impacted with its longitudinal axis parallel to the flat surface and perpendicular to the longitudinal axis of the 15.8mm ± 0.1mm diameter curved surface lying across the center of the test sample. Each sample is to be subjected to only a single impact. 接受撞击的试样,纵轴应与平坦的表面平行并与横放在试样中心的直径 15.8±0.1 毫米弯曲表面的纵轴垂直。每一个试样只经受一次撞击。		Pass 合格
	Requirements 标准要求: 1) Cells external temperature not exceed 170°C. 电池的最高表面温度应不超过 170°C。 2) No disassembly, no rupture and no fire during the test and within six hours after the test. 测试中与测试后 6 小时内无解体、无破裂、无起火。	The samples C011~C020: No leakage, no venting, no disassembly, no rupture and no fire. 编号为 C011~C020 的样品: 无解体、无破裂、无起火现象。 The data is shown in Table T.6 数据见表 T.6	

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 Version: A/2.1

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 7 / 17



	ST/SG/AC.10/11/Rev.7/Section 38.3	
Clause 章节	RequirementsResult标准要求测试结果	Verdict 判定
	Crush (applicable to prismatic, pouch, coin/button cells and cylindrical cells less than 18mm in diameter). 挤压(适用于棱柱形、袋装、硬币/纽扣电池和直径小于 18 毫米的圆柱形电池)。	
	1) A cell or component cell is to be crushed between two flat surfaces. The crushing is to be gradual with a speed of approximately 1.5cm/s at the first point of contact. The crushing is to be continued until the first of the three options below is reached. 将电池或元件电池放在两个平面之间挤压,挤压力度逐渐加大,在第一个接触点上的速度大约为 1.5 厘米/秒。挤压持续进行,直到出现以下三种情况之一: (a) The applied force reaches 13kN ± 0.78kN. 施加的力达到 13 千牛顿±0.78 千牛顿。 (b) The voltage of the cell drops by at least 100mV. 电池的电压下降至少 100 毫伏。 (c) The cell is deformed by 50% or more of its original thickness. 电池变形达原始厚度的 50%或以上。 2). A prismatic or pouch cell shall be crushed by applying the force to the widest side. A button/coin cell shall be crushed by applying the force on its flat surfaces. For cylindrical cells, the crush force shall be applied perpendicular to the longitudinal axis. 棱柱形或袋装电池应从最宽的一面施压。纽扣/硬币形电池应从其平坦表面施压。圆柱形电池应从与纵轴垂直的方向施压。	N/A 不适用
	电池的最高表面温度应不超过 170°C。 2) No disassembly, no rupture and no fire during the test and within six hours after the test. 测试中与测试后 6 小时内无解体、无破裂、无起火。	

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 8 / 17



ST/SG/AC.10/11/Rev.7/Section 38.3			
Clause 章节	RequirementsResult标准要求测试结果	Verdict 判定	
38.3.4.7	Test 7: Overcharge 检测 7: 过度充电		
	1) The charge current shall be twice the manufacturer's recommended maximum continuous charge current. 以制造商建议的最大持续充电电流的两倍对样品充电。 2) The minimum voltage of the test shall be as follows: 试验的最小电压如下: a) When the manufacturer's recommended charge voltage is not more than 18V, the		
	a) When the manufacturer's recommended charge voltage is not more than 18V, the minimum voltage of the test shall be the lesser of two times the maximum charge voltage the battery or 22V. 制造商建议的充电电压不大于 18V 时,试验的最小电压应是电池组最大充电电压的两倍两者中的较小者。 b) when the manufacturer's recommended charge voltage is more than 18V, the minim voltage of the test shall be 1.2 times the maximum charge voltage. 制造商建议的充电电压大于 18V 时,试验的最小电压应为最大充电电压的 1.2 倍。3) Tests are to be conducted at ambient temperature 20±5°C, The duration of the test se 24 hours. 试验应在环境温度(20±5°C)下进行。进行试验的时间应为 24 小时。	F或 22V N/A 不适用	
	Requirements 标准要求: No disassembly and no fire during the test and within seven days after the test. 试验过程中和试验后 7 天内无解体,无起火。		

	T40 F	
38348	Test 8: Forced discharge	8

检测 8: 强制放电

Each cell shall be forced discharged at ambient temperature by connecting it in series with a 12V D.C. power supply at an initial current equal to the maximum discharge current specified by the manufacturer.

每个电池应在环境温度(20±5°C)下与 12V 直流电源串联在起始电流等于制造商给定的最大放电电流的条件下强制放电。

The specified discharge current is to be obtained by connecting a resistive load of the appropriate size and rating in series with the test cell. Each cell shall be forced discharged for a time interval (in hours) equal to its rated capacity divided by the initial test current (in ampere).

将适当大小和额定值的电阻负荷与试验电池串联,计算得出给定的放电电流。对每个电池进行强制放电,放电时间(小时)应等于其额定容量除以初始试验电流(安培)。

Requirements 标准要求:

No disassembly and no fire during the test and within seven days after the test.

试验过程中和试验后7天内无解体,无起火。

The samples C021~C040: no disassembly and no fire. 编号为 C021~C040 的样品: 无解体、无起火现象。
The data is shown in Table T.8
数据见表 T.8

Pass 合格

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 Version: A/2.1

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 9 / 17



ST/SG/AC.10/11/Rev.7/Section 38.3

General terms and definitions 一般术语与定义

Table 38.3.1: Mass loss limit 表 38.3.1: 质量损失限值

Mass M of cell or battery	Mass loss limit		
电池或电池组质量 M	质量损失限值		
M < 1g	0.5%		
1 g ≤ M ≤75 g	0.2%		
M > 75 g	0.1%		

In order to quantify the mass loss, the following procedure is provided:

Mass loss (%) = $(M_1 - M_2)/M_1 \times 100$

质量损失的量化值,可用以下公式计算:

质量损失(%) = (M₁ - M₂)/M₁ × 100

Where M1 is the mass before the test and M2 is the mass after the test. When mass loss does not exceed the values in Table 38.3.1, it shall be considered as "no mass loss".

式中: M1 是试验前的质量, M2 是试验后的质量。如果质量损失不超过表 38.3.1 所列的数值, 应视为"无质量损失"。

Leakage means the visible escape of electrolyte or other material from a cell or battery or the loss of material (except battery casing, handling devices or labels) from a cell or battery such that the loss of mass exceeds the values in Table 38.3.1.

渗漏是指可以看到的电解<mark>液或者其他物质从电池或</mark>电池组中漏出,或电池或电池组中的物质损失(不包括电池外壳、搬运装置、或标签),质量损失超过表 **38.3.1** 所列的数值。

Venting means the release of excessive internal pressure from a cell or battery in a manner intended by design to preclude rupture or disassembly.

排气是指按设计方式释放电池或电池组内部过高的压力,防止其破裂或解体。

Disassembly means a vent or rupture where solid matter from any part of a cell or battery penetrates a wire mesh screen (annealed aluminium wire with a diameter of 0.25 mm and grid density of 6 to 7 wires per cm) placed 25 cm away from the cell or battery.

解体是指排气或破裂使电<mark>池或电池组任何部</mark>分的固体物质穿过放在离电池或电池 25 cm 处的丝网筛(直径 0.25 mm 的软铝丝,网格密度每厘米 6 至 7 条铝丝)。

Rupture means the mechanical failure of a cell container or battery case induced by an internal or external cause, resulting in exposure or spillage but not ejection of solid materials.

破裂是指内部或外部原因引起的电池容器或电池组外壳机械损坏,造成内装物暴露或溢出,但无固体喷射。

Fire means that flames are emitted from the test cell or battery.

起火是指试验电池或电池组有火焰冒出。

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 *Version: A/2.1*

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 10 / 17



Test Data 检测数据

Table T.1 Altitude simulation (表 T.1) 高度模拟

Test		Pre-tes	t 试验前	After test 试验后				
sample status 检测样品 状态	No. 编号	Mass 质量 (g)	Voltage 电压 (V)	Mass 质量 (g)	Voltage 电压 (V)	Mass loss 质量损失 (%)	Change ratio 电压比(%)	Status 结果
First cycle,	C001	39.339	4.19	39.339	4.19	0.000	100.00	Pass 合格
fully	C002	39.348	4.19	39.348	4.19	0.000	100.00	Pass 合格
charged state	C003	39.410	4.18	39.409	4.18	0.003	100.00	Pass 合格
首次循环	C004	39.568	4.19	39.568	4.19	0.000	100.00	Pass 合格
满电状态	C005	39.415	4.19	39.415	4.18	0.000	99.76	Pass 合格
25th cycle,	C006	39.325	4.19	39.325	4.19	0.000	100.00	Pass 合格
fully	C007	39.333	4.18	39.333	4.18	0.000	100.00	Pass 合格
charged state 25 次循环	C008	39.402	4.19	39.402	4.19	0.000	100.00	Pass 合格
	C009	39.554	4.19	39.553	4.18	0.003	99.76	Pass 合格
满电状态	C010	39.405	4.19	39.405	4.19	0.000	100.00	Pass 合格

Notes 注释: Ambient temperature 环境温度: 23.5°C。

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire. And change ratio is not less than 90 %. 检测后,样品无渗漏、无排气、无解体、无破裂和无起火。电压比不小于 90 %。

Table T.2 Thermal test (表 T.2) 温度试验

Test		Pre-tes	t试验前	After test 试验后		N. 77	7	
sample status 检测样品 状态	No. 编号	Mass 质量 (g)	Voltage 电压 (V)	Mass 质量 (g)	Voltage 电压 (V)	Mass loss 质量损失 (%)	Change ratio 电压比(%)	Status 结果
First cycle,	C001	39.3 <mark>39</mark>	4.19	39.332	4.14	0.018	98.81	Pass 合格
fully	C002	39.348	4.19	39.339	4.15	0.023	99.05	Pass 合格
charged state	C003	39.409	4.18	39.402	4.14	0.018	99.04	Pass 合格
首次循环	C004	39.568	4.19	39.560	4.15	0.020	99.05	Pass 合格
满电状态	C005	39.415	4.18	39.408	4.13	0.018	98.80	Pass 合格
25th cycle,	C006	39.325	4.19	39.314	4.14	0.028	98.81	Pass 合格
fully	C007	39.333	4.18	39.323	4.13	0.025	98.80	Pass 合格
charged state	C008	39.402	4.19	39.392	4.15	0.025	99.05	Pass 合格
25 次循环	C009	39.553	4.18	39.544	4.13	0.023	98.80	Pass 合格
满电状态	C010	39.405	4.19	39.397	4.14	0.020	98.81	Pass 合格

Notes 注释: Ambient temperature 环境温度: 24.2°C。

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire. And change ratio is not less than 90 %. 检测后,样品无渗漏、无排气、无解体、无破裂和无起火。电压比不小于 90 %。

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, Chin-中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 11 / 17



Table T.3 Vibration (表 T.3) 振动

Table 1.5 Vibration (表 1.5) 脈勾								
Test		Pre-test 试验前		After test 试验后			1.08000 (11)	
sample status 检测样品 状态	No. 编号	Mass 质量 (g)	Voltage 电压 (V)	Mass 质量 (g)	Voltage 电压 (V)	Mass loss 质量损失 (%)	Change ratio 电压比(%)	Status 结果
First cycle,	C001	39.332	4.14	39.332	4.14	0.000	100.00	Pass 合格
fully	C002	39.339	4.15	39.337	4.15	0.005	100.00	Pass 合格
charged state	C003	39.402	4.14	39.402	4.13	0.000	99.76	Pass 合格
首次循环	C004	39.560	4.15	39.559	4.15	0.003	100.00	Pass 合格
满电状态	C005	39.408	4.13	39.408	4.13	0.000	100.00	Pass 合格
25th cycle,	C006	39.314	4.14	39.314	4.14	0.000	100.00	Pass 合格
fully	C007	39.323	4.13	39.323	4.12	0.000	99.76	Pass 合格
charged state 25 次循环 满电状态	C008	39.392	4.15	39.391	4.15	0.003	100.00	Pass 合格
	C009	39.544	4.13	39.544	4.13	0.000	100.00	Pass 合格
	C010	39.397	4.14	39.397	4.13	0.000	99.76	Pass 合格

Notes 注释: Ambient temperature 环境温度: 23.2°C。

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire. And change ratio is not less than 90 %. 检测后,样品无渗漏、无排气、无解体、无破裂和无起火。电压比不小于 90 %。

Table T.4 Shock (表 T.4) 冲击

Test sample status 检测样品 状态	No. Mass 质量 (g)	Pre-tes	st 试验前 After test 试验后					
		质量	Voltage 电压 (V)	Mass 质量 (g)	Voltage 电压 (V)	Mass loss 质量损失 (%)	Change ratio 电压比(%)	Status 结果
First cycle,	C001	39. <mark>332</mark>	4.14	39.332	4.14	0.000	100.00	Pass 合格
fully	C002	39.3 <mark>37</mark>	4.15	39.336	4.15	0.003	100.00	Pass 合格
charged state	C003	39.402	4.13	39.402	4.13	0.000	100.00	Pass 合格
首次循环	C004	39.559	4.15	39.559	4.14	0.000	99.76	Pass 合格
满电状态	C005	39.408	4.13	39.408	4.13	0.000	100.00	Pass 合格
25th cycle,	C006	39.314	4.14	39.314	4.14	0.000	100.00	Pass 合格
fully	C007	39.323	4.12	39.323	4.12	0.000	100.00	Pass 合格
charged state	C008	39.391	4.15	39.391	4.15	0.000	100.00	Pass 合格
25 次循环	C009	39.544	4.13	39.543	4.12	0.003	99.76	Pass 合格
满电状态	C010	39.397	4.13	39.397	4.13	0.000	100.00	Pass 合格

Notes 注释: Ambient temperature 环境温度: 23.8°C。

After the test, there is no leakage, no venting, no disassembly, no rupture and no fire. And change ratio is not less than 90 %. 检测后,样品无渗漏、无排气、无解体、无破裂和无起火。电压比不小于 90 %。

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 *Version: A/2.1*

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 12 / 17



Table T.5 External short circuit (表 T.5) 外部短路

Test sample statusNo.检测样品状态编号		Maximum external temperature (°C) 表面最高温度(°C)	Status 结果
	C001	88.2	Pass 合格
First cycle, fully	C002	89.3	Pass 合格
charged state	C003	92.5	Pass 合格
首次循环满电状态	C004	94.6	Pass 合格
	C005	89.9	Pass 合格
	C006	93.6	Pass 合格
25th cycle, fully	C007	96.4	Pass 合格
charged state	C008	89.7	Pass 合格
25 次循环满电状态	C009	97.2	Pass 合格
	C010	95.3	Pass 合格

Notes 注释: Ambient temperature 环境温度: 57.0°C。

Test sample external temperature does not exceed 170°C and there is no disassembly, no rupture and no fire during the test and within six hours after the test.

检测样品表面温度不超过 170°C,检测中与检测后 6 小时内无解体、无破裂、无起火。

Table T.6 Impact (表 T.6) 撞击

Test sample status 检测样品状态	No. 编号	Maximum external temperature (°C) 表面最高温度(°C)	Status 结果
	C011	95.6	Pass 合格
First cycle, 50%	C012	94.2	Pass 合格
charged state	C013	97.5	Pass 合格
首次循环 50%充电状态	C014	102.3	Pass 合格
	C015	104.5	Pass 合格
	C016	98.2	Pass 合格
25th cycle, 50%	C017	105.4	Pass 合格
charged state	C018	99.7	Pass 合格
25次循环50%充电状态	C019	106.4	Pass 合格
	C020	103.6	Pass 合格

Notes 注释: Ambient temperature 环境温度: 24.1°C。

Test sample external temperature does not exceed 170°C and there is no disassembly, no rupture and no fire during the test and within six hours after the test.

检测样品表面温度不超过 170°C, 检测中与检测后 6 小时内无解体、无破裂、无起火。

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 *Version: A/2.1*

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 13 / 17



Table T.7 Overcharge (表 T.7) 过充电

Not applicable 不适用

Table T.8 Forced discharge (表 T.8) 强制放电

Test sample status	No.	Status
检测样品状态	编号	结果
	C021	Pass 合格
	C022	Pass 合格
	C023	Pass 合格
	C024	Pass 合格
First cycle, fully discharged state	C025	Pass 合格
首次循环完全放电状态	C026	Pass 合格
	C027	Pass 合格
	C028	Pass 合格
	C029	Pass 合格
	C030	Pass 合格
	C031	Pass 合格
	C032	Pass 合格
	C033	Pass 合格
	C034	Pass 合格
25th cycle, fully discharged state	C035	Pass 合格
25 次循环完全放电状态	C036	Pass 合格
	C037	Pass 合格
	C038	Pass 合格
	C039	Pass 合格
	C040	Pass 合格

Report No.: CMC220609011-1

Notes 注释: Ambient temperature 环境温度: 23.3°C。

There is no disassembly and no fire during the test and within seven days after the test.

样品在检测中和检测后7天内无解体、无起火。

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 Version: A/2.1

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 14 / 17



Main Test Apparatus 主要试验仪器设备清单

	Item 编号	Equipment name 设备名称	Model 型号	Cal. date 校准日期	Due. date 有效期至
\boxtimes	CMC-YQ-001	Programmable Temp.& Humi Chamber 可程式恒温恒湿试验箱	ZZ-K01B	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-005	Battery Test System 电池测试系统	ACTS-20V10A	2022-04-13	2023-04-12
	CMC-YQ-006	Battery Extrusion Testing machine 温控型电池挤压试验机	GX-5067-TSM	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-010	Battery short-circuit tester 温控型电池短路试验机	GX-6055-B5HL	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-011	Battery weight impact testing machine 电池重物冲击试验机	ZZ-A11	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-012	Low Altitude Simulation Tester 电池低压高空模拟试验机	GX-3020-ZC80	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-014	Vibration test instrument 电磁式振动试验机	EV206VT650	2022-03-24	2023-03-23
\boxtimes	CMC-YQ-015	Vertical Shock Test Instrument 机械式冲击试验机	SKT50	2022-03-24	2023-03-23
\boxtimes	CMC-YQ-016-1	Data Collector 数据采集器	34970A	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-019-1	DC POWER 直流电源	PSW80-40.5	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-044-1	Temperature & humidity monitoring intelligent terminal 温度&湿度智能监控终端	ZL-TH10TP	2022-04-13	2023-04-12
	CMC-YQ-021	Electronic platform scale 电子台秤	TCS-200KG	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-022	Electronic Balance 电子天平	JCS-6=5103W	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-023	Digital caliper 数显卡尺	MNT-150	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-025	Digital Multimeter 数字万用表	FLUKE-17B+	2022-04-13	2023-04-12
\boxtimes	CMC-YQ-028	Programmed DC Electronic Load 程控直流电子负载	SJ8512B	2022-04-13	2023-04-12
	CMC-YQ-029	Timer 秒表	XL-009A	2022-04-13	2023-04-12
	CMC-YQ-079-1	Battery Test equipment 电池测试设备	CE-7002-500V300A -R28GC	2022-02-24	2023-02-23
\boxtimes	CMC-YQ-037	Temperature and humidity barometer 温湿度气压表	(980-1050)kPa	2022-04-13	2023-04-12
	CMC-YQ-080	Battery Test equipment 电池测试设备	CE-7002-500V600A -R28GC	2022-02-24	2023-02-23
100000	Used equipment 使 Unused equipment				


101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 *Version: A/2.1*

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 15 / 17




Photos of Samples

样品照片

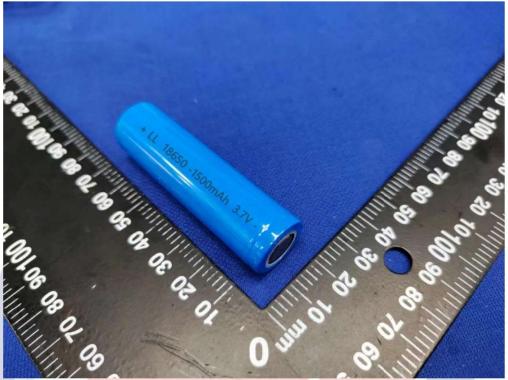

Picture 1. Front view of cell 图片 1. 电池前视图

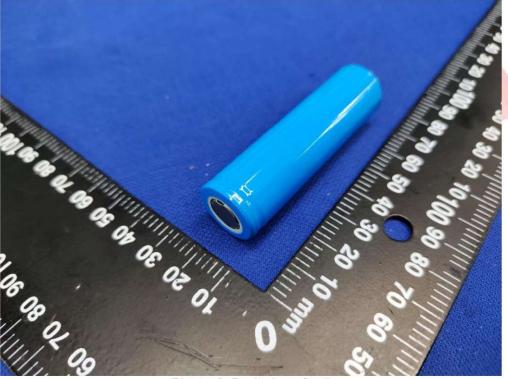

Picture 2. Back view of cell 图片 2. 电池后视图

101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China 中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101 Version: A/2.1

400-1668-320 info@cmczj-lab.com www.cmczj-lab.com 16 / 17



Important

注意事项

- 1. The test report is invalid if it is not affixed the official seal of the laboratory to it. 检测报告无本实验室公章(或检验检测专用章)无效。
- 2. Copies of the test report without the official seal of the laboratory are invalid. 复制检测报告未重新加盖本实验室公章(或检验检测专用章)无效。
- 3. It is forbidden to copy the test report partially without the written approval of the laboratory.

未经本实验室书面批准不得部分复制检测报告。

4. The test report is invalid without the signatures of Approver, Reviewer and Testing engineer.

检测报告无检测、审核、批准人签名无效。

- 5. The test report is invalid if it is blotted out.
 - 检测报告涂改无效。
- 6. Objections to the test report must be submitted to CMC Testing International (Shenzhen)
 Co., Ltd. within 15 days.

对检测报告若<mark>有异议,应于收到报告之日起十五天内向众检检验认证(</mark>深圳)有限公司提出。

- The test report is valid for the tested samples only.
 - 本检测报告仅对检测样品负责。
- 8. As for the Ver<mark>dict, "--" means "no need for judgment"</mark>, "P" means "pass", "F" means "fail" and "N/A" means "not applicable".

判定栏中"--"表示"不需要判定","P"表示"通过","F"表示"不通过","N/A"表示"不适用"。

*** End of Report ***

*** 报告结束 ***

Testing laboratory: CMC Testing International (Shenzhen) Co., Ltd.

检测单位: 众检检验认证 (深圳) 有限公司

Address: 101, Building B, Kaihuimao Industrial Park, Liyuan Road, Heping Community, Fuhai Street, Baoan District, Shenzhen, Guangdong, China

地址:中国广东省深圳市宝安区福海街道和平社区荔园路恺辉茂工业园厂房 B 栋 101

Tel (电话): 400-1668-320 E-mail: info@cmczj-lab.com http://www.cmczj-lab.com

17 / 17